UNCLASSIFIED

AD NUMBER
AD876334
LIMITATION CHANGES

TO:

Approved for public release; distribution is unlimited.

FROM:

Distribution authorized to U.S. Gov't. agencies and their contractors; Critical Technology; SEP 1970. Other requests shall be referred to Office of Naval Research, 875 North Randolph Street, Arlington VA 22203-1995. This document contains export-controlled technical data.

AUTHORITY

ONR ltr, 13 Jan 1972

THIS PAGE IS UNCLASSIFIED

AD876334

MONSANTO/WASHINGTON UNIVERSITY
ONR/ARPA ASSOCIATION

STUDIES OF STRESS-STRAIN BEHAVIOR OF SAN/GLASS BEAD COMPOSITES ABOVE THE GLASS TRANSITION TEMPERATURE

BY

M. NARKIS
L. NICOLAIS

Wash D.C. 20360

PROGRAM MANAGER

ROLF BUCHDAHL

DDC
RECEIVED
NOV 9 1970
A

MONSANTO RESEARCH CORPORATION
A SUBSIDIARY OF MONSANTO COMPANY

800 N. LINDBERGH BOULEVARD   ST. LOUIS, MISSOURI 63166

M

23

NOTICES

AD- 768

HPC 70-118

STUDIES OF STRESS-STRAIN BEHAVIOR OF SAN/GLASS BEAD
COMPOSITES ABOVE THE GLASS TRANSITION TEMPERATURE

BY

M. NARKIS
L. NICOLAIS

SEPTEMBER 1970

FOREWORD

STUDIES OF STRESS-STRAIN BEHAVIOR OF SAN/GLASS BEAD
COMPOSITES ABOVE THE GLASS TRANSITION TEMPERATURE

M. Narkis* and L. Nicolais**

Materials Research Laboratory
Washington University
St. Louis, Missouri 63130

ABSTRACT

Relaxation and stress-strain behavior of SAN/glass bead composites is studied above the glass transition temperature. The strain imposed on the polymeric matrix of the composite is defined as $\varepsilon_p = \varepsilon_c/(1 - \phi^{1/3})$. Stress relaxation data for the filled polymer which is independent of strain can be calculated by multiplying the relaxation modulus (at a certain strain) by $(1 + \varepsilon_p)$. Stress-strain curves at constant strain rate and for different concentrations of the filler can be shifted to form a master curve independent of filler content if the tensile stress is plotted versus ε_p. The relaxation modulus increases with increasing the filler concentration and can be predicted by a modified Kerner equation at 110°C.

*Presently with the Centre for Industrial Research, POB 311, Haifa, Israel

**On leave from the Laboratorio di Ricerca su Tecnologia dei Polimeri e Reologia del C.N.R. Napoli, Italy.

STUDIES OF STRESS-STRAIN BEHAVIOR OF SAN/GLASS BEAD COMPOSITES ABOVE THE GLASS TRANSITION TEMPERATURE

M. Narkis and L. Nicolais

Materials Research Laboratory
Washington University
St. Louis, Missouri 63130

Introduction

In a recent publication [1] the behavior of SAN(styrene-acrylonitrile copolymer)/glass bead composites in the glassy region was described. The behavior of similar composites in the region above the glass transition temperature is discussed here. The quantitative analysis of stress-strain data for even unfilled polymers at high extensions is not straightforward. Obviously, it is much more complicated to analyze similar data for filled polymers. Smith [2] suggested a simple equation for calculation of strain in the continuous polymeric matrix as a function of the composite strain and the filler content. Essentially the same equation is used in this work and the significance of the strain in the polymer is shown by using a semi-empirical quantitative analysis.

Composites of a thermoplastic matrix and particulate fillers have been studied by several researchers above the glass transition temperature. Landel [3] studied the dynamic mechanical properties of PIB/glass bead composites. In his work, the temperature shift factors for the composites were nearly identical to those for the unfilled polymer. The Guth-Smallwood equation [4,5] was found appropriate for the prediction of the stiffness in the long-time region. The dewetting time in stress relaxation

experiments for plasticized PVC/CaCO$_3$ composites has been shown to depend on the filler concentration, decreasing as the filler content is increased [6]. The effect of filler concentration on tensile properties of highly filled, cross-linked polyurethane rubber was also studied [7]. In this work the mechanical behavior at low extensions can be represented by a generalized Maxwell model and the modulus increase with increasing the filler content is satisfactorily described by an empirical modification of the Eilers equation [8].

Experimental

Preparation techniques for SAN(LUSTRAN A, Monsanto Co.)/glass bead composites were described in a previous paper [1]. Test specimens were 6 inch long strips, 1/2 inch wide and 0.1 inches thick. A gage of 2" was used in all tests.

Results and Discussion

It has been shown that the relaxation modulus of an unfilled polysulfone is time and strain dependent [9]. However, if strain is defined as $\ell_n(\ell/\ell_o)$ and a correction is made for the decrease of cross-sectional area, then the relaxation modulus is only time dependent at any given temperature. Other definitions must be used for filled polymers.

Smith [2] has shown by a simple theoretical analysis that

$$\varepsilon_c = \varepsilon_p \ (1 - 1.105\phi^{1/3})\qquad(1)$$

where ϕ is the volume fraction of filler, ε_p is the strain in the polymer and ε_c is the strain imposed on the composite. The

data obtained in the present work were analyzed by using the equation $\varepsilon_c = \varepsilon_p (1 - K\phi^{1/3})$ and the best fit was obtained for K equal to unity, thus the definition of strain in the polymer in the present work is as follows:

$$\varepsilon_p = \frac{\varepsilon_c}{1 - \phi^{1/3}} \qquad (2)$$

The relaxation modulus for filled polymers depends on time and strain at a constant temperature. Analysis of experimental data shows that the ratio of two relaxation moduli (for a certain composite) at a common time but at different strains is practically independent of time within the range of strain and time that were studied. Therefore, stress relaxation curves for a filled polymer at different strains ε_c can be shifted along the modulus axis to a reference curve at a reference strain. This procedure has been used in the past for unfilled polymers [10].

Further analysis of the experimental data has shown that the above mentioned modular ratio is a function of the strains imposed on the polymer. This function can be described as follows

$$\frac{\left| E_{c\varepsilon}(t) \right|_2}{\left| E_{c\varepsilon}(t) \right|_1} = \frac{1 + \left(\varepsilon_p\right)_1}{1 + \left(\varepsilon_p\right)_2} \qquad (3)$$

The term $(1 + \varepsilon_p)$ apparently accounts for the reduction in cross-sectional area of the polymer that is "isolated" from the composite.

In Table 1 calculated ϵ_p values, according to Equation (2), and $(1 + \epsilon_p)$ values, to be used in Equation (3), are shown for two filler concentrations and for several levels of composite strain.

In Table 2 relaxation data for $\phi = 0.213$ and for three different strains are shown. The modular ratios are practically independent of time. The average experimental ratios are in good agreement with the predicted ratios as calculated with Equation (3). A similar conclusion can be drawn from Table 3 which summarizes experimental and calculated results for $\phi = 0.427$.

In light of this conclusion the relaxation modulus of the composite $E_c(t)$ independent of strain is defined as follows

$$E_c(t) = \left(1 + \frac{\epsilon_c}{1 - \phi^{1/3}}\right) E_{c\epsilon}(t) = \left(1 + \epsilon_p\right) E_{c\epsilon}(t) \qquad (4)$$

In Table 4 the stress relaxation modulus, independent of strain, is tabulated for experimental data at three different strains. For linearly viscoelastic bodies, stress-strain curves at a constant strain rate can be calculated from relaxation data [9,11] by using the following equation [12,13]:

$$f(t) = \dot{\epsilon} \int_{-\infty}^{\ell nt} tE(t)d\ell nt \qquad (5)$$

Equation (5) was found appropriate for unfilled polysulfone and polycarbonate above their glass transition temperature if proper definitions of strain and strain rate are used [9]. In the present case, the relaxation data given in Table 4 is believed to be strain independent and one can try to use it for calculation of stress-strain curves. In order to extend the relaxation data given in Table 4 to the region of shorter times, which is necessary for the integration of Equation (5), stress relaxation data at 118°C were shifted to the reference curve at 127°C. The strain independent stress relaxation moduli in the time range from 0.025 to 1 min. is given in Table 5. By using the data given in Tables 4 and 5, the integral in Equation (5) can be evaluated. Calculated stress-strain curves at two strain rates are shown in Figure 1 along with the experimental curves. The calculated and experimental curves have similar shapes, however the agreement is not entirely satisfactory. Undoubtedly, additional comparison of calculated stress-strain curves according to Equation (5) with experimental curves is required for filled polymers.

In Figure 2 stress-strain curves for different concentrations of glass beads at a constant strain rate are shown. At a given strain, ε_c, the stress increases with increasing filler concentration. This is typical for filled polymers above their glass transition temperature. In Figure 3 the data of Figure 2 are replotted as the stress versus strain in the polymer. Analysis of these curves shows that the ratio of two stresses for different glass bead concentrations, but at a common ε_p, is independent of ε_p. According

to this result the curves can be shifted along the stress axis
to produce a master curve. In Figure 3 the stress-strain curves
are also shifted to the curve for the unfilled SAN and are in a
good agreement with the experimental points for the unfilled
polymer. The shift factors a_c are 1.0, 1.3, 1.95 and 4.5 for 0.0,
0.213, 0.427 and 0.536 volume fraction of glass beads respectively.
Attempts to predict the values of a_c have been unsuccessful so far.

The effect of glass bead concentration on the relaxation
modulus was studied at 110°C, which is close to the transition
temperature of the filled polymer . In Figure 4 the relaxation
modulus at 110°C is plotted versus time for different concentrations
of glass beads. The modulus at a certain time increases with
increasing the filler content as predicted by Kerner [14]. A
good agreement between the experimental and calculated relative
moduli was obtained by a modified Kerner equation which was
recently suggested by Lewis and Nielsen [15]. The modified
Kerner equation was confirmed for the relative storage modulus
in shear of epoxy/glass bead composites by these authors.

Assuming that $E_c/E_p \neq G_c/G_p$, the modified Kerner equation
can be written as follows

$$\frac{E_c}{E_p} = \frac{1 + AB\phi}{1 - B\psi\phi} \tag{6}$$

where

$$A = \frac{7 - 5\nu_p}{8 - 10\nu_p} = 1.5 \qquad\qquad B = \frac{G_g/G_p - 1}{G_g/G_p + A} = 1$$

and

$$\psi = \left[1 + \left(\frac{1 - \phi_m}{\phi_m^2} \right) \phi \right] \tag{7}$$

or

$$\psi\phi = 1 - \exp\left(\frac{-\phi}{1 - \phi/\phi_m} \right) \tag{8}$$

The function ψ is the modification of Lewis and Nielsen which accounts for the maximum packing fraction ϕ_m. Poisson's ratio for the polymer ν_p above its glass transition is equal to 0.5. The ratio of the modulus of glass beads G_g to the modulus of the rubbery polymer G_p is very large compared to unity, thus $B \doteq 1$. ϕ_m is equal to 0.64.

Equation (8) was used for the epoxy/glass bead composites while for the SAN/glass bead composites Equation (7) is found to be more satisfactory. In Figure 4 calculated $E_p(t)$ values from data on filled SAN is shown to be in a good agreement with the experimental relaxation modulus for the unfilled polymer. At 127°C the modular ratio is found to be time dependent which cannot be predicted by any of the theoretical reinforcement equations.

Acknowledgment

References

1. L. Nicolais and M. Narkis, "Studies of Stress Strain Behavior of SAN/Glass Bead Composites in the Glassy Region," submitted for publication.

2. T. L. Smith, _Trans. Soc. Rheol._, 3, 113 (1959).

3. R. F. Landel, _Trans. Soc. Rheol._, 2, 53 (1958).

4. E. Guth, _J. Appl. Phys._, 16, 20 (1945).

5. H. M. Smallwood, _J. Appl. Phys._, 15, 758 (1944).

6. R. Sabia and F. R. Eirich, _J. Polymer Sci._, 2, 1909 (1964).

7. K. W. Bills, Jr., K. H. Sweeny and F. S. Salcedo, _J. Appl. Polymer Sci._, 4, 259 (1960).

8. H. Eilers, _Kolloid-Z._, 97, 313 (1941).

9. M. Narkis, "Calculation of Stress-Strain Curves from Relaxation Data in the Rubbery-Flow Region," submitted for publication.

10. R. D. Andrews, N. Hofman-Bang and A.V. Tobolsky, _J. Polymer Sci._, 3, 669 (1948).

11. T. L. Smith, _Trans. Soc. Rheol_, 6, 61 (1962).

12. R. Sips, _J. Polymer Sci._, 5, 69 (1950).

13. J. D. Ferry, _Viscoelastic Properties of Polymers_, Wiley, New York, 1961.

14. E. H. Kerner, _Proc. Phys. Soc._, B 69, 808 (1956).

15. T. B. Lewis and L. E. Nielsen, _J. Appl. Polymer Sci._, 14, 1449 (1970).

Table 1: Calculated ϵ_p values for two filler concentrations and different composite strains, ϵ_c.

ϵ_c	$1 - \phi^{1/3}$ $\begin{array}{l}\phi = 0.213 \\ = 0.403\end{array}$		$1 - \phi^{1/3}$ $\begin{array}{l}\phi = 0.427 \\ = 0.247\end{array}$	
	ϵ_p	$1 + \epsilon_p$	ϵ_p	$1 + \epsilon_p$
0.05	-	-	0.202	1.202
0.10	0.248	1.248	0.404	1.404
0.20	0.496	1.496	0.808	1.808
0.30	0.744	1.744	-	-

Table 2: The effect of strain on relaxation modulus, $E_\epsilon(t)$ at 127°C. Modulus units are $(\text{dynes/cm}^2)10^{-6}$. $\phi = 0.213$.

Min.	$E_{0.1}(t)$	$E_{0.2}(t)$	$E_{0.3}(t)$	$\dfrac{E_{0.1}(t)}{E_{0.2}(t)}$	$\dfrac{E_{0.1}(t)}{E_{0.3}(t)}$	$\dfrac{E_{0.2}(t)}{E_{0.3}(t)}$
1	7.10	6.05	5.75	1.17	1.23	1.05
2	5.50	4.65	4.15	1.18	1.32	1.12
3	4.60	3.90	3.30	1.18	1.40	1.18
5	3.65	3.10	2.65	1.18	1.37	1.17
10	2.55	2.15	1.80	1.19	1.41	1.19
20	1.60	1.40	1.15	1.14	1.39	1.22
40	1.07	0.90	0.77	1.19	1.39	1.17
	Average			1.18	1.36	1.16
	Predicted (Eq. 3)			1.20	1.40	1.17

Table 3: The effect of strain on relaxation modulus $E_\epsilon(t)$ at 127°C. Modulus units are (dynes/cm^2) x 10^{-6}. $\phi = 0.427$.

Min.	$E_{0.05}(t)$	$E_{0.1}(t)$	$E_{0.2}(t)$	$\dfrac{E_{0.05}(t)}{E_{0.1}(t)}$	$\dfrac{E_{0.05}(t)}{E_{0.2}(t)}$	$\dfrac{E_{0.1}(t)}{E_{0.2}(t)}$
1	17.9	15.6	11.0	1.15	1.62	1.42
2	11.7	10.0	7.50	1.17	1.55	1.33
3	9.60	8.06	5.95	1.19	1.62	1.36
5	7.20	6.03	4.55	1.19	1.58	1.32
10	4.40	3.74	2.83	1.17	1.55	1.32
20	2.60	2.24	1.76	1.16	1.48	1.28
40	1.45	1.29	1.00	1.13	1.45	1.28
		Average		1.17	1.57	1.33
		Predicted (Eq.3)		1.17	1.51	1.29

Table 4: Strain independent modulus calculated from relaxation data at different strains at 127°C. $\phi = 0.217$. Modulus units are (dynes/cm^2) x 10^{-6}.

Min.	$1.248 \times E_{0.1}(t)$	$1.496 E_{0.2}(t)$	$1.744 E_{0.3}(t)$
1	8.85	9.05	10.0
2	6.85	6.95	7.20
3	5.75	5.85	5.75
5	4.55	4.65	4.62
10	3.18	3.21	3.14
20	2.00	2.10	2.00
40	1.33	1.35	1.34

Table 5: $E_c(t)$ as a function of time at 127°C. $\phi = 0.213$.
Units are (dynes/cm^2) x 10^{-6}

Min.	0.025	0.05	0.1	0.15	0.25	0.5	0.75	1
$E_c(t)$	22.4	18.8	15.8	14.2	12.5	10.3	9.13	8.85

List of Figures

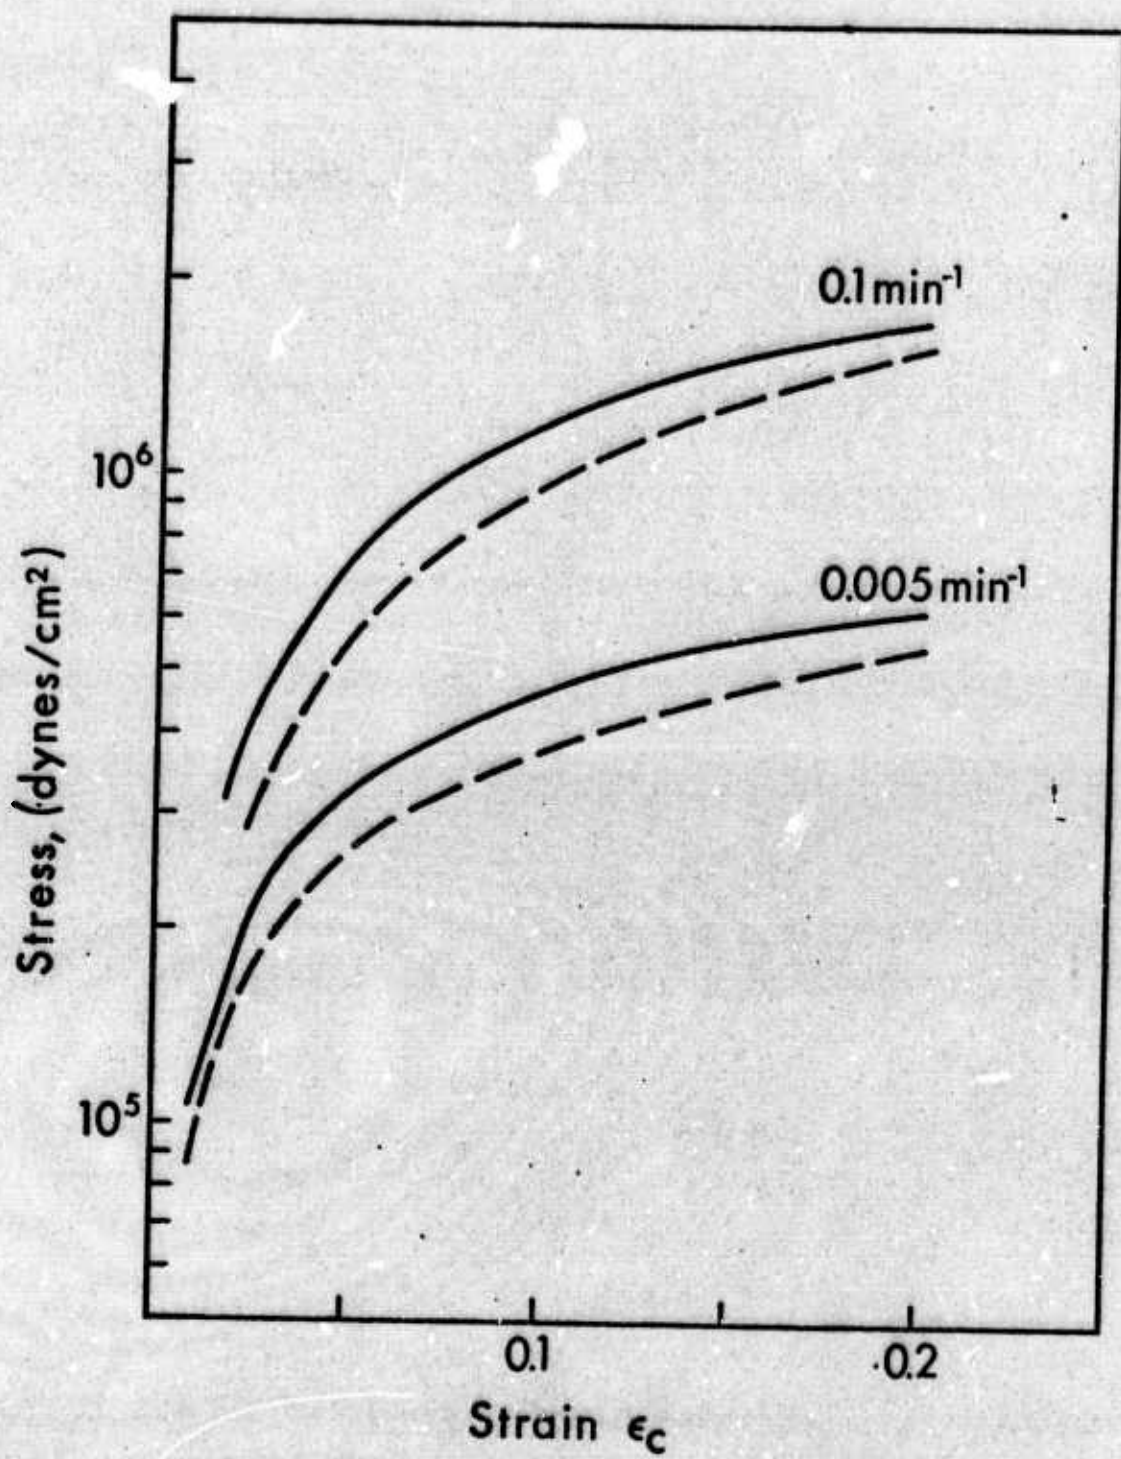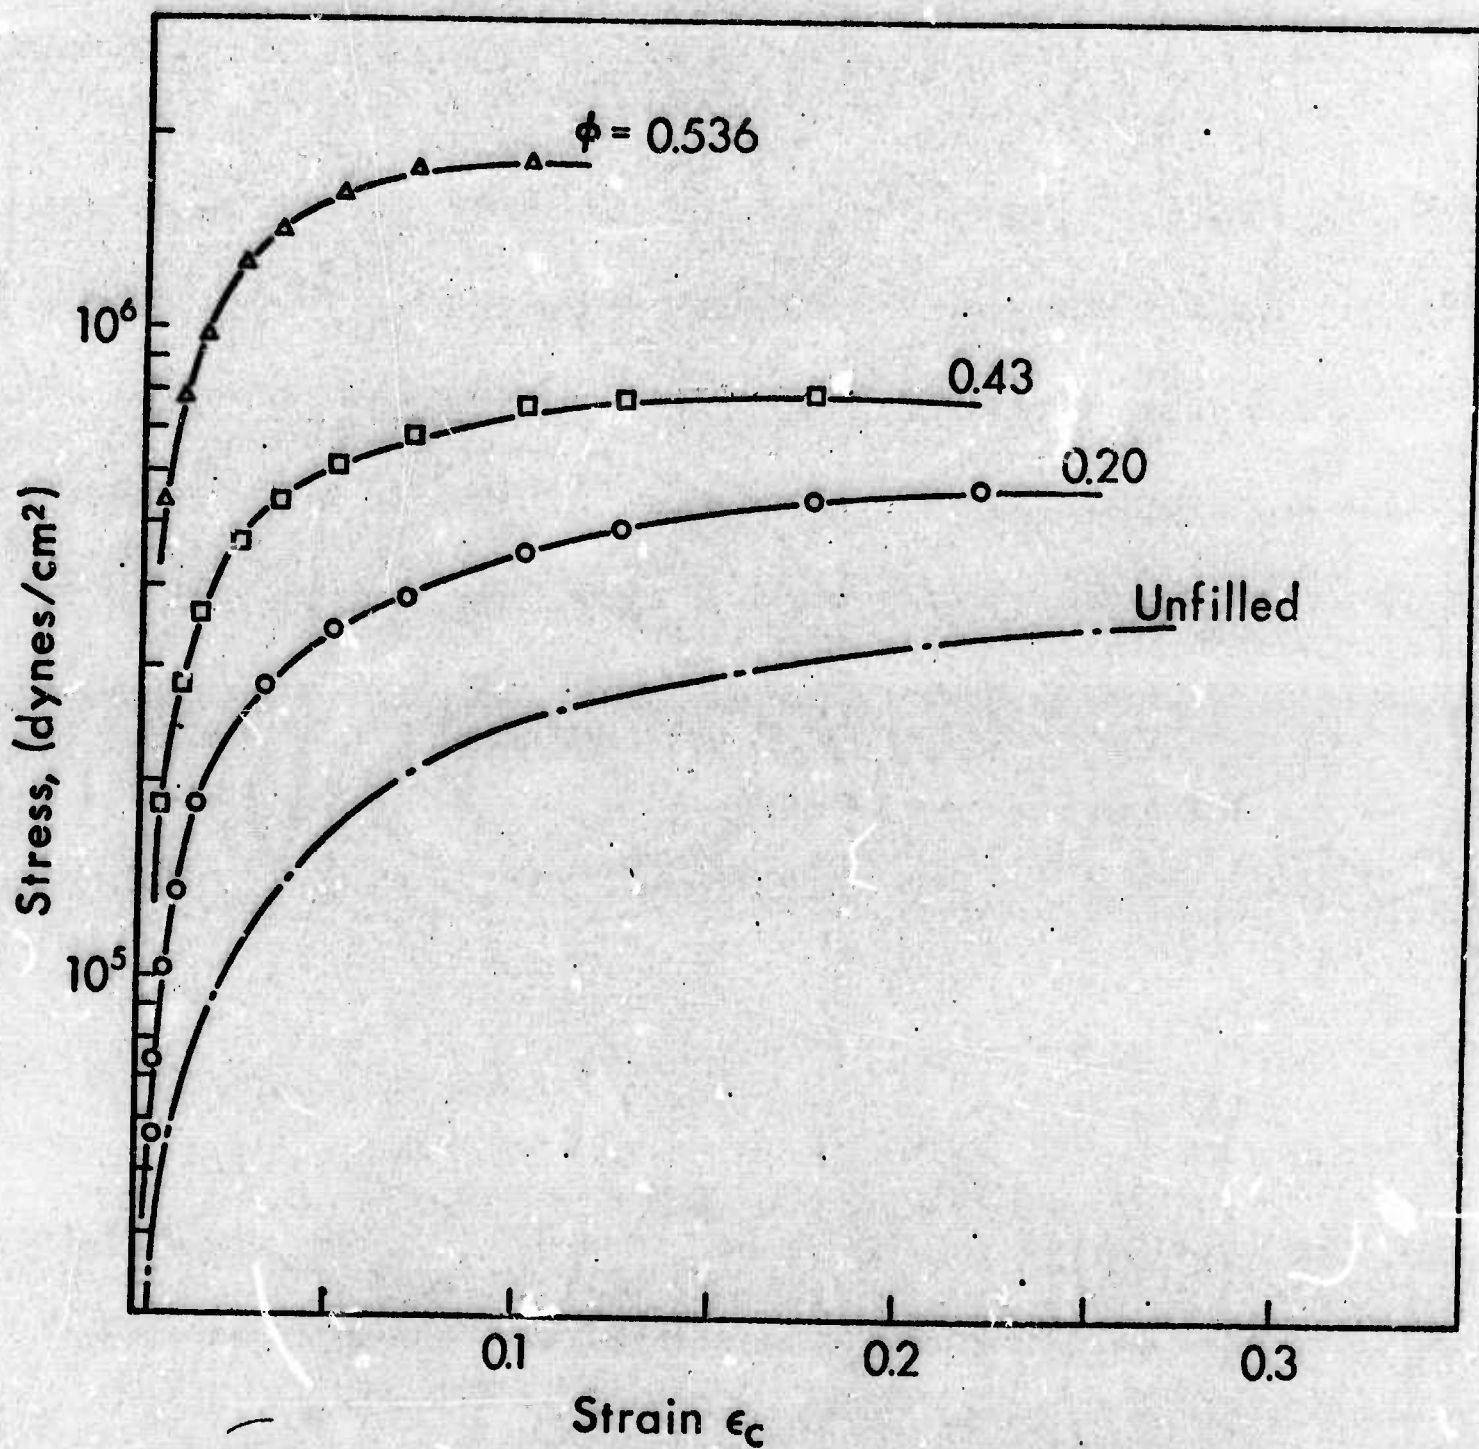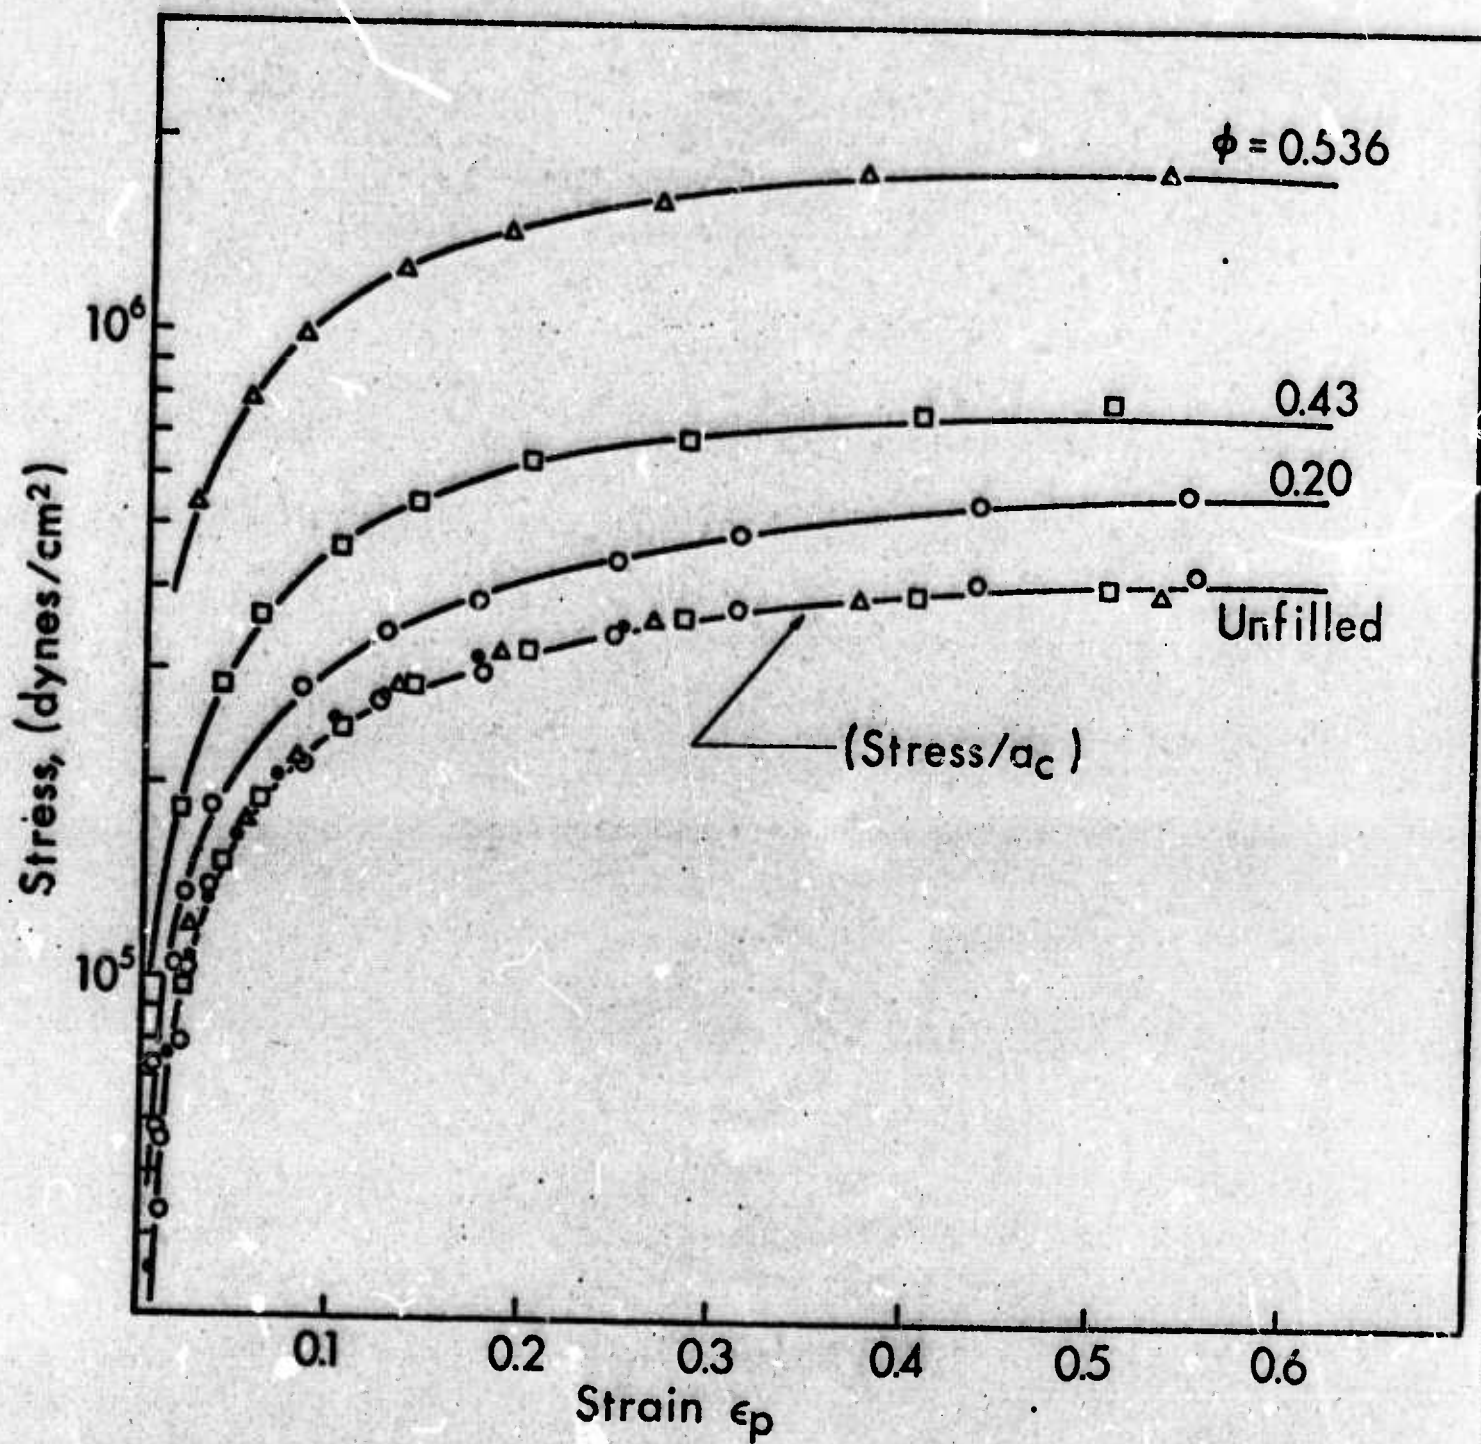Figure 1

Figure 2

Figure 3

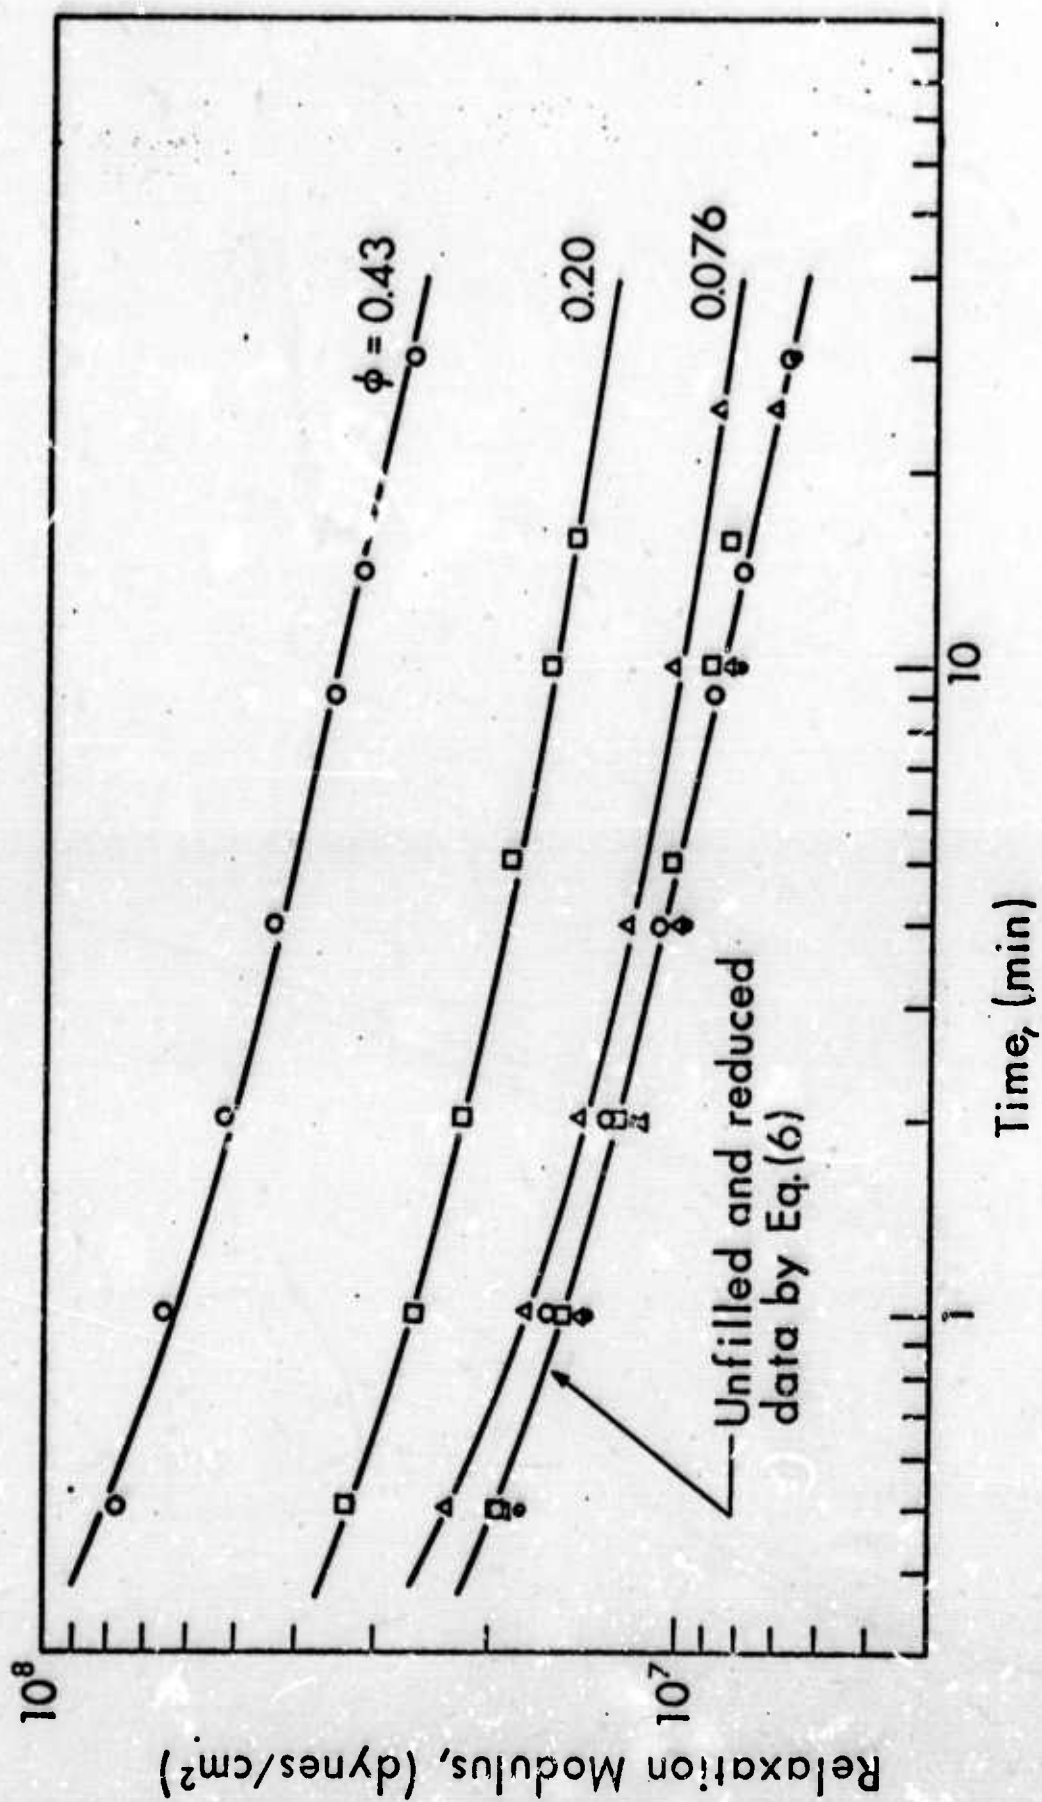Figure 4

DOCUMENT CONTROL DATA - R & D

(Security classification of title, body of abstract and indexing annotation must be entered when the overall report is classified)

1. ORIGINATING ACTIVITY (Corporate author)	2a. REPORT SECURITY CLASSIFICATION
Monsanto Research Corporation	UNCLASSIFIED
	2b. GROUP

3. REPORT TITLE

Studies of Stress-Strain Behavior of SAN/Glass Bead
Composites Above the Glass Transition Temperature

4. DESCRIPTIVE NOTES *(Type of report and inclusive dates)*

5. AUTHOR(S) *(First name, middle initial, last name)*

M. Narkis and L. Nicolais, Washington University

6. REPORT DATE	7a. TOTAL NO. OF PAGES	7b. NO. OF REFS
September 1970	26	15

8a. CONTRACT OR GRANT NO.	9a. ORIGINATOR'S REPORT NUMBER(S)
N00014-67-C-0218	
b. PROJECT NO.	HPC 70-118
c.	9b. OTHER REPORT NO(S) *(Any other numbers that may be assigned this report)*
d.	

10. DISTRIBUTION STATEMENT

This document is subject to special export controls and each transmittal
to foreign governments or foreign nationals may be made only with prior
approval of the Director of Material Sciences, Office of Naval Research.

11. SUPPLEMENTARY NOTES	12. SPONSORING MILITARY ACTIVITY
	Office of Naval Research Washington, D. C. 20360

13. ABSTRACT

Relaxation and stress-strain behavior of SAN/glass bead composites
is studied above the glass transition temperature. The strain imposed
on the polymeric matrix of the composite is defined as $\epsilon_p = \epsilon_0/(1 - \phi^{1/3})$.
Stress relaxation data for the filled polymer which is independent of
strain can be calculated by multiplying the relaxation modulus (at a
certain strain) by $(1 + \epsilon_p)$. Stress-strain curves at constant strain
rate and for different concentrations of the filler can be shifted
to form a master curve independent of filler content if the tensile
stress is plotted versus ϵ_p. The relaxation modulus increases
with increasing the filler concentration and can be predicted by a
modified Kerner equation at 110°C.

14. KEY WORDS	LINK A		LINK B		LINK C	
	ROLE	WT	ROLE	WT	ROLE	WT
composites						
styrene-acrylonitrile						
strain-rate						
relaxation modulus						
rubbery flow						
time-temperature superposition						